

Antiferromagnetic vortex core in HTSC studied by spatially-resolved NMR

Ken-ich Kumagai^a, Kosuke Kakuyanagi^a, Yuji Matsuda^b, Tadashi Hasegawa^c

^a*Division of Physics, Graduate School of Science, Hokkaido University, Sapporo 060-0180, Japan*

^b*Institute for Solid State Physics, University of Tokyo, Kashiwa, 277-8581, Japan*

^c*Institute for Materials Research, Tohoku University, Sendai, 980-8577, Japan*

Abstract

Spatially-resolved NMR is used to probe the magnetism in the vortex state of $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+\delta}$ ($T_c=85$ K). We found that (1): T_1^{-1} at ^{205}Tl is extremely enhanced toward to the vortex core, (2): T_1 process becomes largely-inhomogeneous in the vortex state, and (3): the T -dependence of T_1^{-1} at the vortex core region shows a peak at $T=20$ K. These results indicate a clear evidence of the AF order inside the vortex core. The suppression of the d -wave superconducting order parameter leads to the nucleation of islands with the local AF order.

Key words: NMR ;vortex core ;High- T_c superconductor; antiferromagnetic order

How antiferromagnetism emerges when the d -wave superconducting (SC) order parameter is suppressed is a fundamental problem in the physics of high- T_c superconductors (HTSC)[1]. Closely related to this problem, the microscopic structure of the vortex core turns out to be a very interesting subject, since many unexpected nature has been observed experimentally. A new class of theories have emphasized the importance of the magnetism arising from strong electron correlations for accounting the microscopic vortex core structure.

Neutron scattering experiments on $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ have reported recently that an applied magnetic field enhances the AF correlation in the SC state [2]. However, the relation between the observed AF static ordering and magnetic excitations within the vortex core is still not clear, because the neutron experiments lack spatial resolution.

Recent experimental [3–5] and theoretical [6] NMR studies have established that the frequency dependence of nuclear spin-lattice relaxation rate, T_1^{-1} in the vortex state serves as a probe for the low energy excitation

spectrum. Up to now, however, all of these spatially-resolved NMR measurements have been carried out at the ^{17}O sites [3–5], at which the AF fluctuations are filtered.

In this paper we obtain local information on the AF correlations in the spatially-different regions of the vortex lattice by the spatially resolved NMR imaging experiment on ^{205}Tl -nuclei in nearly optimal-doped $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+\delta}$. This attempt is particularly suitable for the above purpose because T_1^{-1} at the Tl-site can monitor AF fluctuations sensitively. This is owing to the fact that the Tl atoms are located just above the Cu atom and there exist large transferred hyperfine interactions between Tl and Cu nuclei through apical oxygen (see the inset of Fig. 1). On the basis of the results of the NMR imaging, we have established a clear evidence of the AF vortex core state [7].

High quality $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+\delta}$ with $T_c=85$ K has been synthesized under a high oxygen pressure atmosphere. NMR measurements were carried out on the c -axis oriented polycrystalline powder in the external field along the c -axis. As shown in Fig. 1, a clear asymmetric pattern of the NMR spectrum, which originates from the local field distribution associated with the Abrikosov

¹ E-mail: kumagai@phys.sci.hokudai.ac.jp

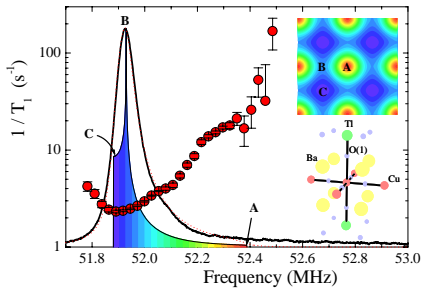


Fig. 1. ^{205}Tl -NMR spectrum and frequency dependence of $^{205}\text{Tl}^{-1}$ (filled circles) at 5 K. The thin solid line depicts the histogram at particular local fields of the Redfield pattern with $\xi=18\text{\AA}$ and $\lambda_{ab}=1700\text{\AA}$. The upper inset shows the image of the field distribution in the vortex square lattice. A-position represents the vortex core, B is at the field corresponding to the saddle point of the vortices, and C-point is at the center of the vortex square lattice. The lower inset shows the crystal structure of $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+\delta}$.

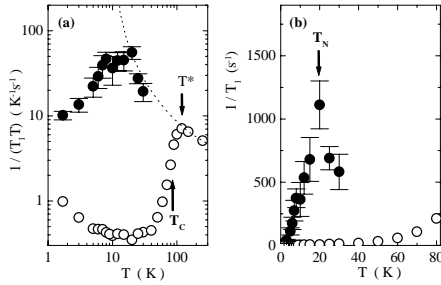


Fig. 2. Temperature dependence of $(^{205}\text{Tl}T)^{-1}$ (a) and $^{205}\text{Tl}^{-1}$ (b) of ^{205}Tl in $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+\delta}$. The filled circles represent the data at the vortex core and open circles represent the data at the saddle point. In (a) $T^* \sim 120\text{ K}$ is the pseudogap temperature, and $T_c \sim 85\text{ K}$ is the SC transition temperature. The dotted line represents the Curie-Weiss law which is determined above T^* . In (b), T_N is the temperature at which $^{205}\text{Tl}^{-1}$ at the vortex core exhibits a sharp peak.

vortex lattice (the Redfield pattern), is observed below 50 K.

For ^{205}Tl with nuclear spin of $I=1/2$, the recovery curve from the saturation of the nuclear magnetization fits well to a single exponential relation. In the vortex state, on the other hand, the feature of the recovery curves is strongly positional-dependent, and shows a $\sqrt{\tau}$ functional form at the core region. We defined T_1 as the time required for the nuclear magnetization to decay by a factor $1/e$,

Figure 1 shows the frequency dependence of $^{205}\text{Tl}^{-1}$ at 5 K. On scanning from the outside into the core (C \rightarrow B \rightarrow A), $^{205}\text{Tl}^{-1}$ increases rapidly after showing a minimum near the saddle point (B). The magnitude of $^{205}\text{Tl}^{-1}$ in the core region is approximately 80 times larger than that near the saddle point. This large enhancement of $^{205}\text{Tl}^{-1}$ is in striking contrast to

$^{17}\text{Tl}^{-1}$ at ^{17}O sites reported in $\text{YBa}_2\text{Cu}_3\text{O}_7$ [3,4] and $\text{YBa}_2\text{Cu}_4\text{O}_8$ [5],

Figures 2 shows the T -dependences of $(^{205}\text{Tl}T)^{-1}$ and $^{205}\text{Tl}^{-1}$ within the core and at the saddle point. Well above T_c , $(^{205}\text{Tl}T)^{-1}$ obeys the Curie-Weiss law. $(^{205}\text{Tl}T)^{-1}$ shows a broad peak at $T = T^* (\sim 120\text{ K})$, and then decreases rapidly without showing any anomaly associated with the SC transition at T_c , similar to other HTSC, which can be attributed to the pseudogap. Below 40 K, $(^{205}\text{Tl}T)^{-1}$ in the SC region is reduced largely and is nearly T -independent down to 4 K.

The T -dependence of $^{205}\text{Tl}^{-1}$ at the vortex core regime contains some key features for understanding the core magnetism. $1/^{205}\text{Tl}$ exhibits a sharp peak at $T = T_N (= 20\text{ K})$. Below T_N , $(^{205}\text{Tl})^{-1}$ decreases rapidly with decreasing T . The sharp peak of $^{205}\text{Tl}^{-1}$ at T_N seems to support the occurrence of a local AF ordering. We also point out that the appearance of the local AF ordering is also consistent with the $\sqrt{\tau}$ dependent nuclear magnetization decay curve. In fact, the $\sqrt{\tau}$ dependence has been observed when the microscopic inhomogeneous distribution of T_1^{-1} due to strong magnetic scattering centers is present [8].

In summary, spatially-resolved NMR provide a direct evidence that the AF spin correlation is extremely enhanced in the vortex core region, and in the core region Cu spins, the paramagnetic -AF ordering transition occurs at $T_N = 20\text{ K}$ in $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+\delta}$.

This work has been supported by a Grant-in-Aid from Ministry of Education, Culture, Sports, Science and Technology.

References

- [1] S.C. Zhang, Science 275 (1997) 1089.
- [2] B. Lake, *et al.*, Science **291** (2001) 1759.
- [3] N.J. Curro, C. Milling, J. Hasse, C.P. Slichter, Phys. Rev. B **62** (2000) 3473.
- [4] V. F. Mitrovic, *et al.*, Nature **413**(2001) 501.
- [5] K. Kakuyanagi, K. Kumagai, Y. Matsuda, Phys. Rev. **B65** (2002) 060503(R).
- [6] D.K. Morr R. Wortis, Phys. Rev. B **61**(2000) R882, and D.K. Morr, Phys. Rev. B **63** (2001) 214509.
- [7] K. Kakuyanagi, K. Kumagai, Y. Matsuda, T. Hasegawa, to be published.
- [8] M.R. McHenry, B.G. Silbernagel, J.H. Wernick, Phys. Rev. **B5** (1972) 2958.